



Corrosion Protection with Polymer Liners/Coatings

Presented by Aaron Hoffman

Lewis Concrete Restoration



Discussion Topics

- Functional Polymer Liner/Coatings
- Why use Polymer Liners/Coatings?
- Types of Coatings/Lining Systems
- Comparison
- Summary





Functional – The look of a long-service life 😊





Definition of Protective Coatings or Linings

- By the corrosion protection industry's definition (**NACE**); a coating is a material that is applied up to 0.125 inches (<125 mils) in thickness that develops an adhesive bond with surface of the material to be protected. When a material has been applied to a thickness of more than 0.125 inches (>125 mils) it is designated to be a liner; whether it is in a bonded or an un-bonded condition.





Rule of Thumb

-
- Protective Coating =
 - Applied at approximately 1.0 – 125.0 mils dft.
 - Designed to create a mechanical or chemical bond (adhesion) to the substrate.
 - Protective Lining =
 - Applied at 125.0 – 500.0+ mils dft.
 - Can be bonded or un-bonded

FYI - Some say “Coating on the exterior and Lining on the internal”





Why are Polymer Liners/Coatings Used?

- Functional Protective Barriers
 - Chemical Resistance
 - Abrasion Resistance
 - Impact Resistance
 - High velocity water resistance
- Infiltration Control
 - Seal and protect manhole structure from infiltration from groundwater
- Visual anniversary inspections



Polymer chemistry for the protection of Manholes

- Epoxies
 - Hi-Build reinforced Epoxy (80-250+ mils)
 - Thin Film (20-60 mils)
- Polyurethanes
 - Elastomeric (80-300+ mils)
 - Moisture Curing Thin-Film (10-30 mils)
- Polyurea (80-300+ mils)
 - Pure
 - Hybrid





Epoxy (Thin Film)

Pro

- Long established coating with excellent performance properties to protect structures in industrial environments.
- Thin-film systems applied at 20.0 - 60.0 mils dft.
- Long pot life and can be applied by single leg, conventional airless equipment.

Cons

- Physical properties at the low end of what is normally required for the rehabilitation of degraded manhole structures.
- Multiple coats to meet higher film build requirements
- Can be sensitive to moisture and temperature during application
- Long return to service in wastewater immersion (>24 hours)
- Beware of the applicator!
 - Training, lack of surface preparation knowledge, and use of safety equipment (PPE)






Epoxy (High-Build Reinforced)

Pro

- Excellent Chemical Resistance
- Strong Physical Properties
 - Resistant to hydrostatic pressure due to groundwater
- Application to wet (SSD) concrete
- Good/Excellent adhesion (bond) to the host structure
- Fast return to wastewater service (2-24 hours)
- Typically, trained “Certified Applicators”

Con

- Rigid (Elongation 2%-10%)
- Expert/trained applicators a must!

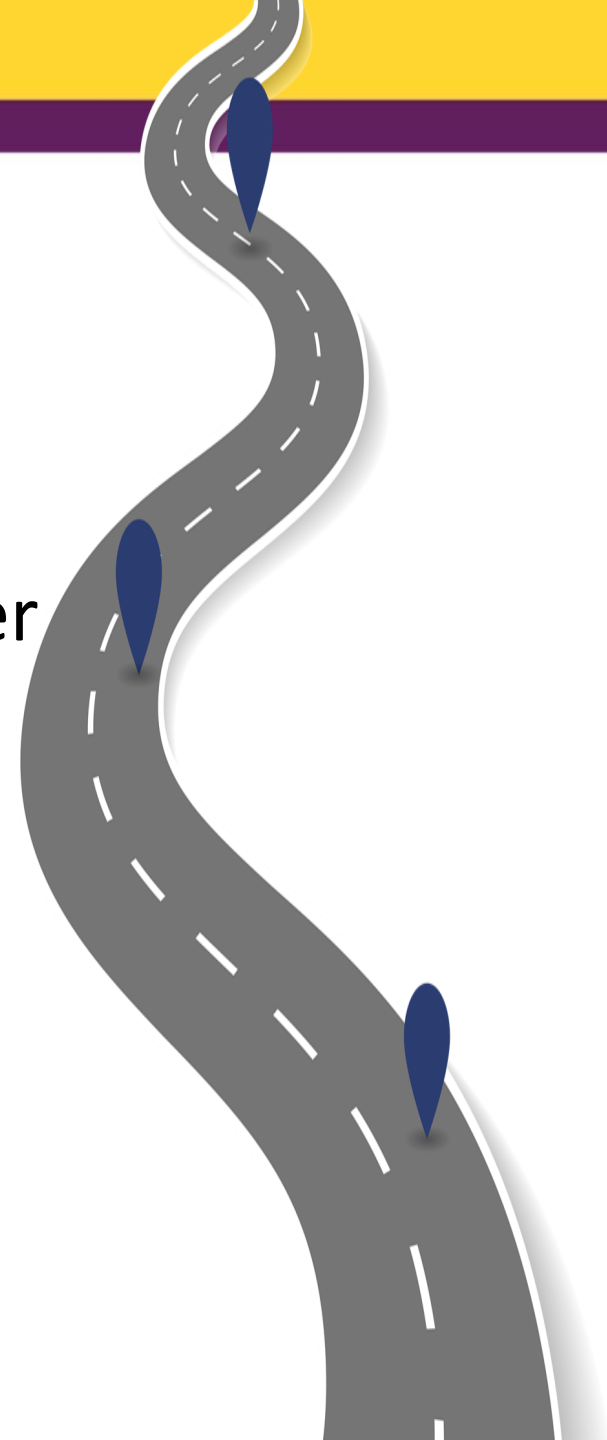




Elastomeric Polyurethane

Pro

- Chemical Resistant
- Flexible and crack bridging (40%-100%)
- Fast cure
- High-Build (30-250+ mils)

Con

- Sensitive to Moisture
- Fair to good adhesion (bond) to the host structure
 - Primer are recommended for underground structures

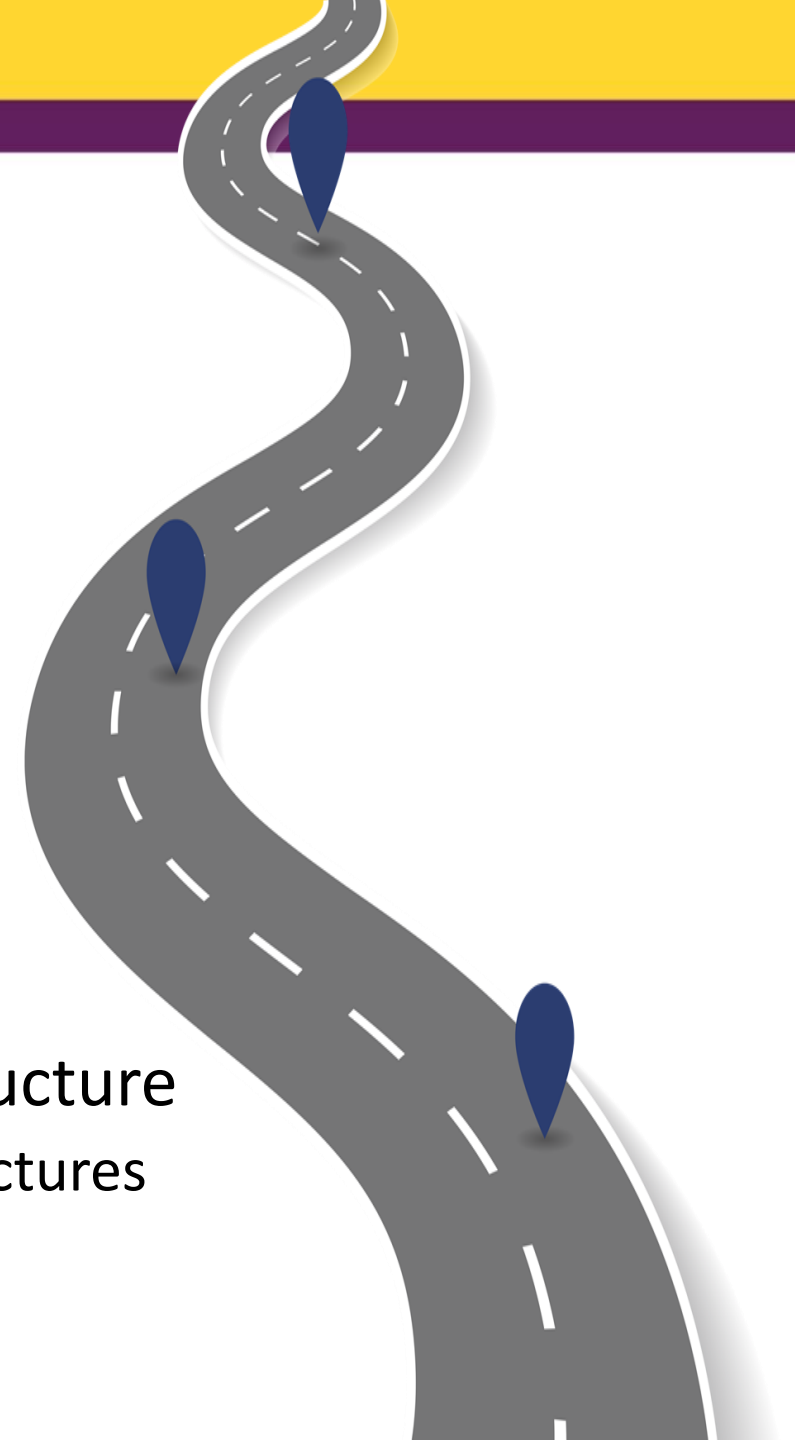




Moisture Curing Polyurethane

Pro

- Single component
- Apply by hand tools or spray methods
- Can be applied at 99% RH

Con

- Very thin-film (10-20 mils)
- Substrate must be visibly dry
- Not for rehabilitation
- Coal-Tar

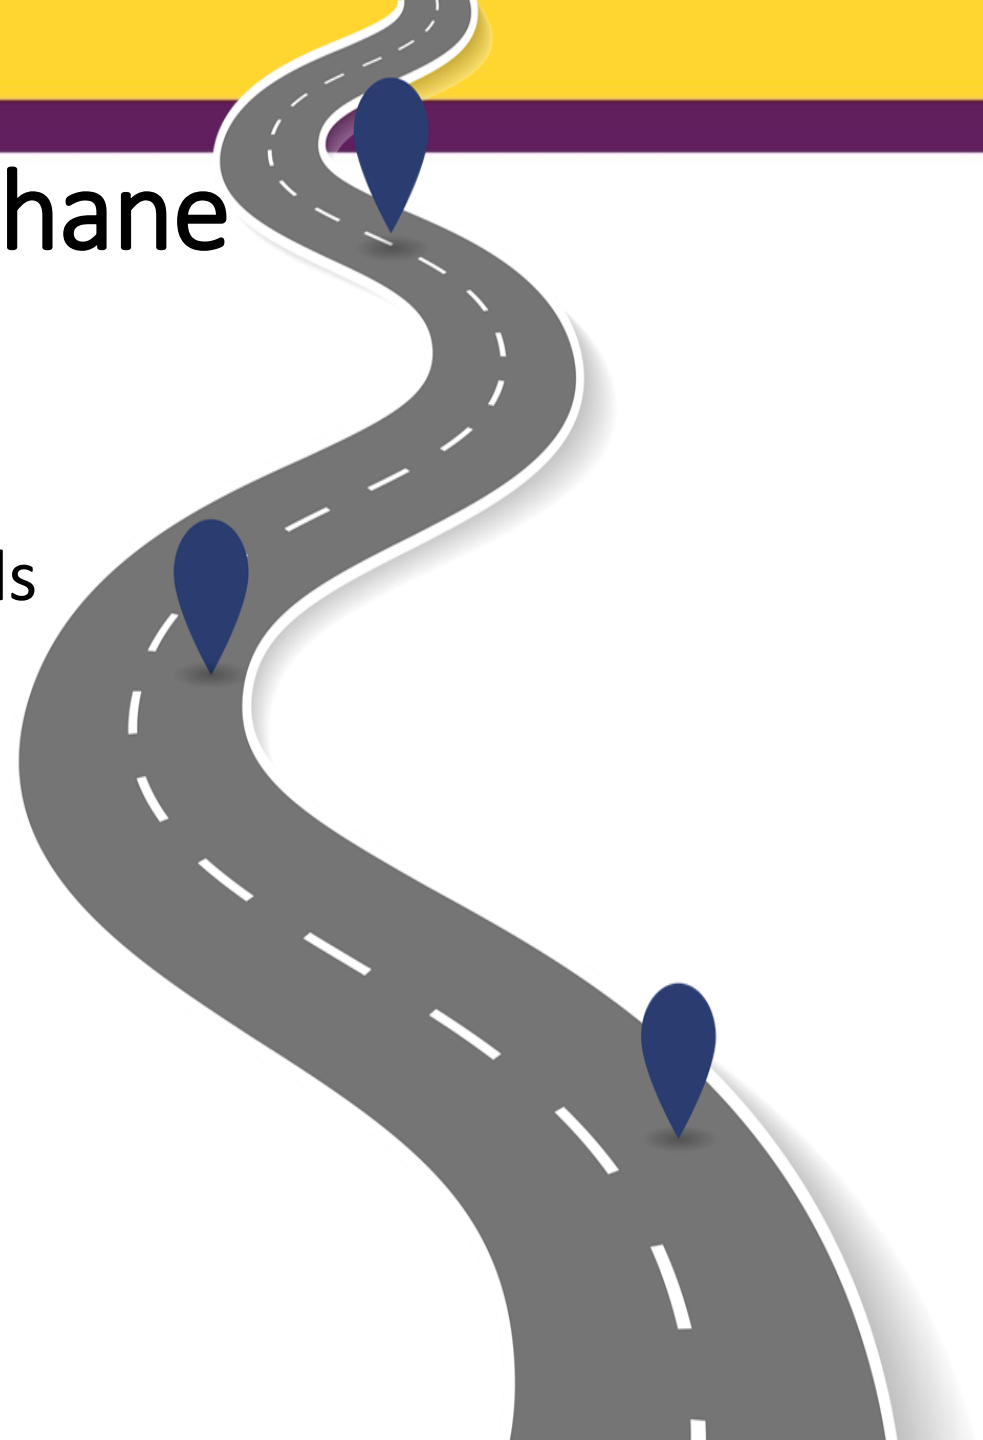




Polyurea – “Pure”

Pro

- Rapid Setting (Tack free 10-30 seconds)
- Flexible and crack bridging (100%-500% tensile elongation)
- Fast return to service
- High-Build (60-500+ mils)
- Good Chemical Resistance
- Can be applied at any ambient temperature (-20°F to 200°F+)

Con

- Fair/Good adhesion to primed concrete
- Sensitive to moisture during application

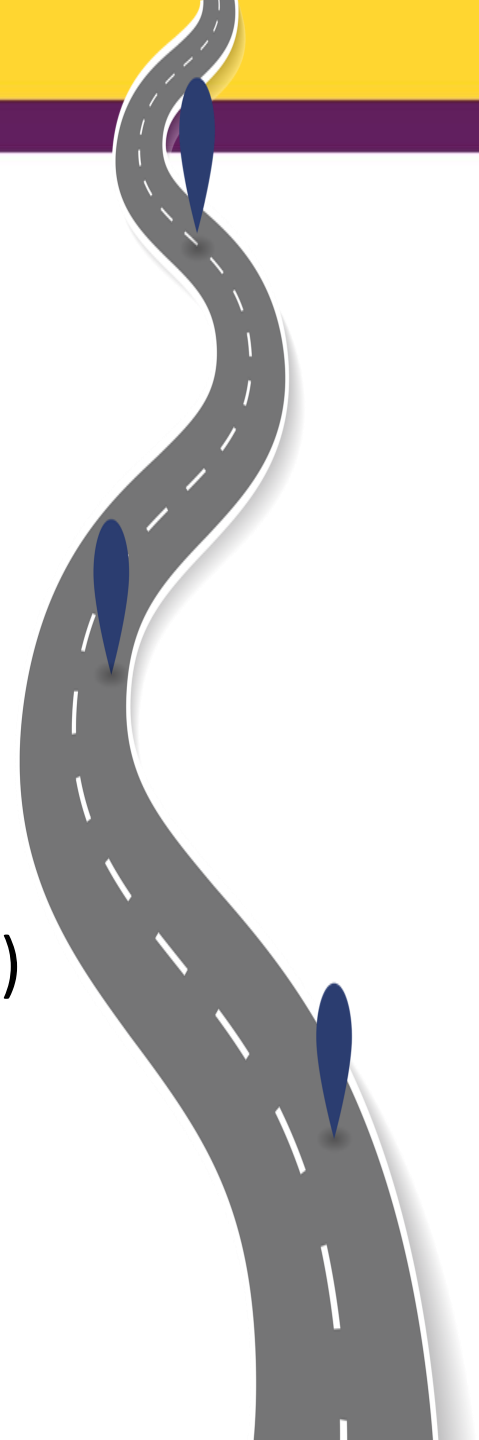




Polyurea - Hybrid

Pro

- Rapid Setting (Tack free 10-30 seconds)
- Flexible and crack bridging (100%-400+% tensile elongation)
- Fast return to service
- High-Build (60-300+ mils)
- Good Chemical Resistance
- Slower cure allows air to escape and reduce pinholes in the film
- Good adhesion to primed concrete

Con

- Fair/Good adhesion to primed concrete
- Sensitive to moisture during application

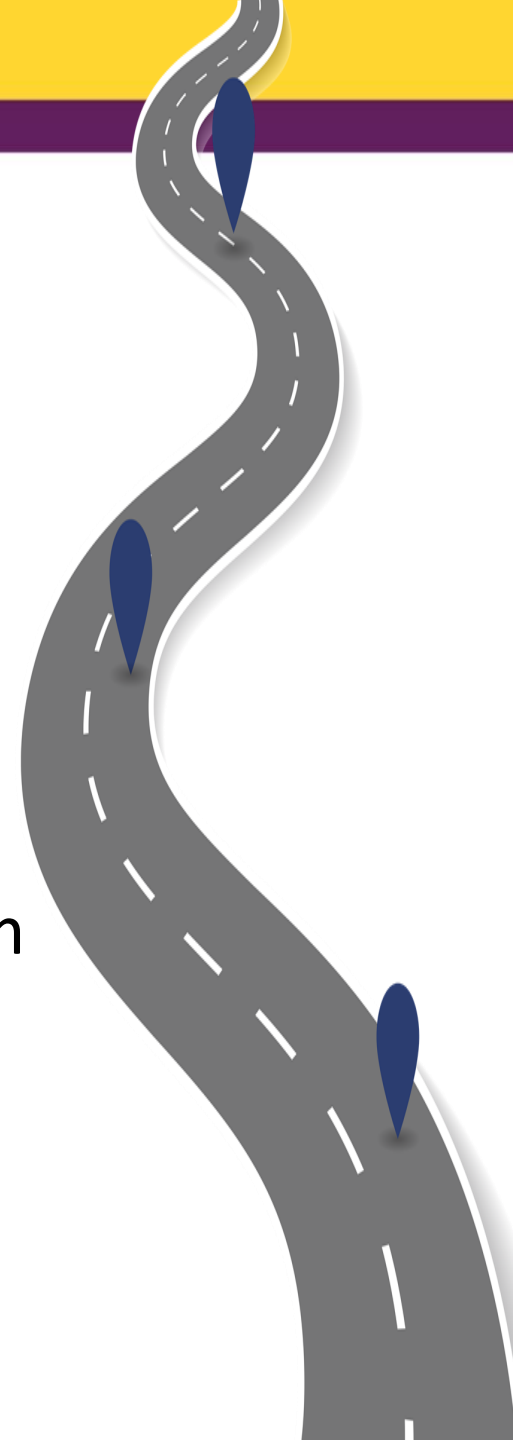



Generic Product Comparison

Characteristics	Epoxy (Thin-Film)	Polyurea	Polyurethane	Hi-Build Epoxy
Adhesion to Dry Concrete	Good	Good	Good	Excellent
Moisture Filled	Not recommended	Good (w/Primer)	Good (w/Primer)	Excellent
Wet (SSD)	Not Recommended	Not recommended	Not recommended	Excellent
Tensile Strength (ASTM D638)	Up to 7,000 psi	2,000-3,500 psi	(Flex)2,000-3,000 psi (Rigid) >7,000 psi	5,000-8,000 psi
Tensile Elongation (ASTM D638)	4%-10%	75%-400%	5%-100%	2%-5%
Chemical Resistance 20% Sulfuric Acid	Poor/Fair	Good	Good	Excellent
Max mils per coat	Up to 50 mils dft.	300+ mils	300+ mils	Up to 250+ mils



However, Choose your Polymer Liner/Coating Wisely

Correct product selection, installation and Inspection can help prevent:

- Polymer coating or liner dis-bonding
- Aggressive corrosion after the failure
- Pinholes & thin coating
- Ground water infiltration issues





Summary



- Polymer Coatings/Liners are protective, functional, barriers against microbial induced corrosion (MIC), abrasion, erosion, and ground water intrusion.
- Polymer Coating/Liners are typically:
 - Epoxy / Fiber-reinforced Hi-Build Epoxy
 - Polyurethane
 - Polyurea
- And...Choose your polymer liner/coating wisely!
 - Know the conditions of sewer collection structures
- Trained/Certified/Approved Applicators a PLUS
- QA/QC Inspections / Third-Party Testing



Thank You

